arXiv:1207.0528v1 [cond-mat.supr-con] 2 Jul 2012

Transition to a Layered Phase-Decoupled Superconducting State in $La_{2-x}Ba_xCuO_4$ Single Crystals Induced by a Strong Transverse Magnetic Field

Z. Stegen,[1] Su Jung Han,[2,3] Jie Wu,[1,2] Genda Gu,[2] Qiang Li,[2] J. H. Park,[1] G. S. Boebinger,[1] and J. M. Tranquada[2]
[1]*National High Magnetic Field Laboratory, Florida State University, Tallahassee, FL 32310*
[2]*Condensed Matter Physics & Materials Science Department,*
Brookhaven National Laboratory, Upton, NY 11973-5000
[3]*Department of Materials Science and Engineering,*
Stony Brook University, Stony Brook, New York 11794, USA

(Dated: July 4, 2012)

We present measurements of the resistivity parallel and perpendicular to the CuO_2 layers in single crystals of $La_{2-x}Ba_xCuO_4$ (LBCO) with $x = 0.095$ as a function of perpendicular magnetic fields up to 35 T. At temperatures below the zero-field superconducting transition of 31.5 K, there is a regime of field strength for which superconducting phase coherence between the layers is destroyed, yet effective coherence is retained within the layers. Evidence that this is an actual state of matter is provided by a well-defined loss of order, indicated by the field dependence of the in-plane resistivity. The behavior of this phase is qualitatively identical to that observed previously for LBCO with $x = 1/8$ in zero field, in which frustration of the interlayer Josephson coupling is associated with spin and charge stripe order.

Unusual superconducting states have been observed [1, 2] in association with the 1/8 anomaly in $La_{2-x}Ba_xCuO_4$ (LBCO) [3, 4]. In this earlier work, the three-dimensional (3D) superconducting transition temperature, T_c, is depressed below 5 K; nevertheless, cooling below ~ 40 K yields an order of magnitude drop in the resistivity parallel to the CuO_2 planes, $\rho_\parallel$. On further cooling, $\rho_\parallel$ decreases in a fashion consistent with that expected for a two-dimensional (2D) superconducting vortex liquid [5], while the resistivity perpendicular to the layers, $\rho_\perp$, remains large; this apparent layered-vortex-liquid (LVL) state is accompanied by anisotropic diamagnetism. Finally, $\rho_\parallel$ extrapolates to zero at ~ 16 K, while $\rho_\perp$ remains finite. Regardless of whether the individual layers develop true superconducting order, one would expect that inevitable Josephson coupling should have driven 3D superconducting order near 40 K where the first strong 2D superconducting correlations appeared [6]. The strong suppression of 3D order indicates that the interlayer Josephson coupling is frustrated for some reason [7–9].

While the frustrated Josephson coupling is surprising, the occurrence of superconducting order in a system of decoupled layers is compatible, in principle, with existing theory [10], at least in the absence of an applied magnetic field. What is more surprising is that both the LVL and the layered phase-decoupled (LPD) superconducting (SC) state survived in a perpendicular magnetic field, $\mu_0 H_\perp$, of at least 3 T. Such a field should easily destroy the order in individual layers [11]. Recently, transport studies of LBCO with $x = 0.095$, a good bulk superconductor, indicated a field-induced LPD-SC state [12, 13]; however, with the limited range of magnetic field used it was not possible to distinguish the thermal variation of the resistivity from the exponential behavior expected for thermally-excited vortex motion [11, 14].

In this letter, we report transport studies of LBCO $x = 0.095$ in $\mu_0 H_\perp$ up to 35 T. The data provide evidence for a high-field thermal crossover from the normal state to an LVL phase, followed at lower temperature by a transition to the LPD-SC. Our results are summarized in Fig. 1. In zero field, the sample has $T_{c0} = 31.5$ K in measurements of both $\rho_\perp$ and $\rho_\parallel$, but the observed transitions separate at finite field. The onset of finite $\rho_\perp$ occurs at $H_c^\perp$, while, as we will explain, phase-decoupling of the layers happens at the slightly higher field H_Q. In contrast, we observe evidence for a phase transition to finite $\rho_\parallel$ at $H_c^\parallel$, with $H_c^\parallel \gg H_c^\perp$. The temperature dependence of $\rho_\parallel$ above $H_c^\parallel$ is similar to that predicted [5, 15] for

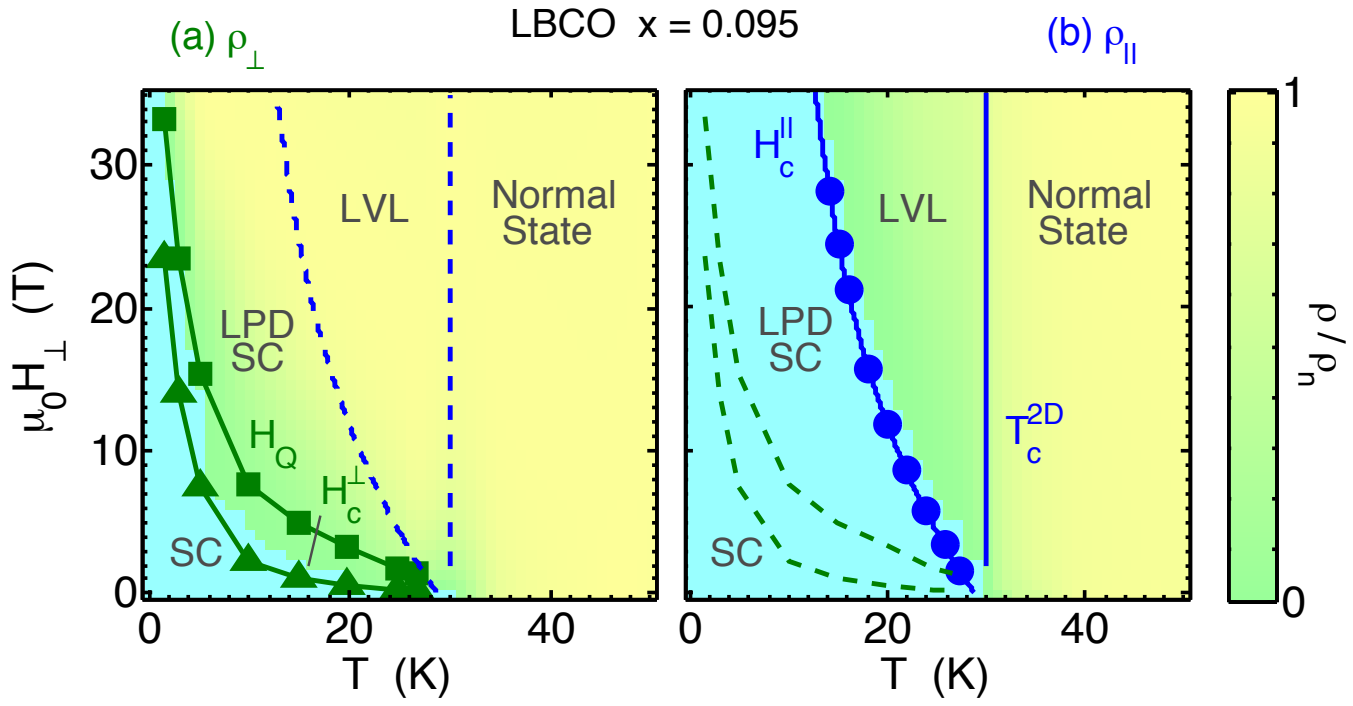

FIG. 1. (color online) Phase diagrams in $H_\perp$-T space obtained from measurements of (a) $\rho_\perp$ and (b) $\rho_\parallel$. In (a), triangles indicate the onset of finite $\rho_\perp$ at $H_c^\perp$; squares denote H_Q corresponding to the interlayer phase-decoupling crossover. In (b), circles indicate onset of finite $\rho_\parallel$ at $H_c^\parallel$; vertical solid line corresponds to T_c^{2D}, the crossover from the layered vortex liquid phase to the normal state. In each panel, the shaded contours correspond to the resistivity normalized to an extrapolation of the normal-state behavior obtained at the maximum field. (Online: $\rho/\rho_n < 10^{-3}$ is cyan.)

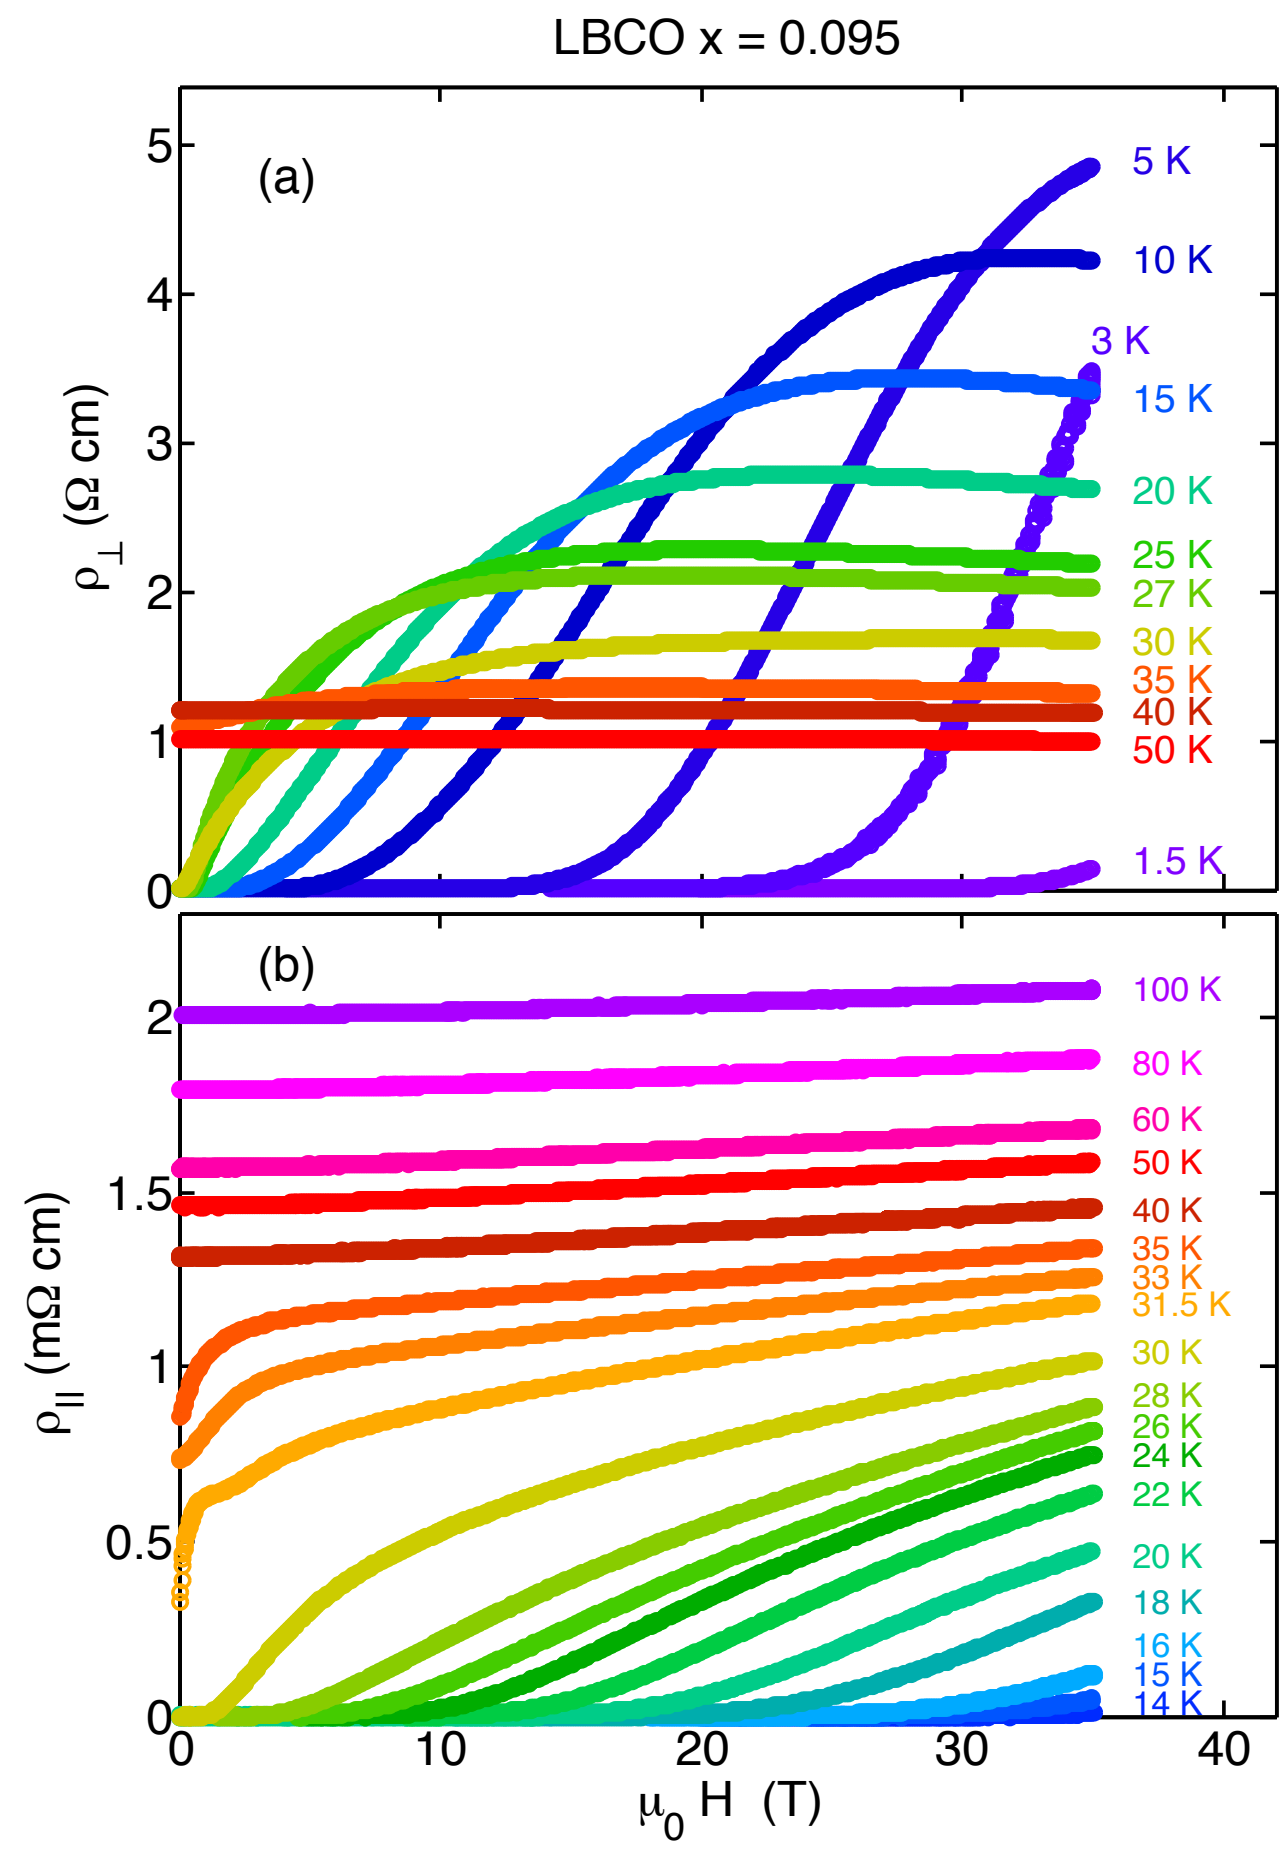

FIG. 2. (color online) Measurements of (a) $\rho_\perp$ and (b) $\rho_\parallel$ as a function of $H_\perp$, obtained at various fixed temperatures as listed in each panel.

a two-dimensional (2D) superconductor above a vortex-antivortex unbinding transition [16, 17], $T_{\rm BKT}$. At $T_c^{\rm 2D}$ there is a crossover to the normal state. The state between H_Q and $H_c^{\parallel}$ we identify as LPD-SC, while the state between $H_c^{\parallel}$ and $T_c^{\rm 2D}$ is identified as the LVL.

The crystals, grown by the traveling-solvent floating-zone method, have been characterized in several previous studies [4, 12, 13, 18]. The present experiments were performed in the 35-T dc magnet at the National High Magnetic Field Laboratory (NHMFL). The crystals for the measurements of $\rho_\perp$ and $\rho_\parallel$ are the same as those used in a previous transport study [12], and the contact configurations are described there. The resistance was measured using an ac resistance bridge with an excitation current of 1 mA. All measurements were done after field-cooling from above T_{c0}. The resulting scans of resistivity vs. $H_\perp$ obtained for a range of temperatures are shown in Fig. 2.

Let us first consider $\rho_\perp(H_\perp)$. For $T \lesssim 30$ K, increasing $H_\perp$ initially causes $\rho_\perp$ to become finite, followed by rapid growth and eventual saturation, followed by a gradual decrease beyond the maximum. Such behavior has been studied previously, especially in $\rm Bi_2Sr_2CaCu_2O_{8+\delta}$ [19, 20] and $\rm Bi_2Sr_{2-x}La_xCuO_{6+\delta}$ [21]. The rise of $\rho_\perp$ with increasing $H_\perp$ is due to suppression of the conduction channel associated with interlayer pair tunneling; on crossing the maximum, single-particle transport dominates [19]. The region of negative magnetoresistance at high field has been attributed to the impact of $H_\perp$ on the pseudogap [20]; reducing the antinodal gap increases the density of normal carriers that can move between planes. Parallels have also been drawn with the field-tuned superconductor-insulator transition observed in disordered thin-films of various metals [22–24]. By this latter analogy, the resistive transition in $\rho_\perp$ can be viewed as a transition to a Cooper pair insulator phase at high $\mu_0 H_\perp$. In our case, the Cooper pairs are localized along the c axis, becoming restricted to the $\rm CuO_2$ layers.

Is it possible to identify a threshold for insulating behavior along the c axis? It has been argued by several groups that the rise in $\rho_\perp$ can be understood in terms of phase fluctuations in the interlayer Josephson junctions due to thermal noise [25–28]. In this interpretation, the relevant quantity is the extensive resistance per Josephson junction. Hettinger *et al.* [28] demonstrated empirically that the effective junction area corresponds to $A = \Phi_0/(B_\perp + B_0)$, where Φ_0 is the flux quantum and B_0 is a parameter. We have shown in [12] that this approach gives a good description of the evolution of $\rho_\perp(T, H_\perp)$ in our sample for $T < T_{c0}$ with $B_\perp \approx \mu_0 H_\perp$ and $B_0 = 2.2$ T. The effective junction resistance is then $R_\perp = \rho_\perp s/A$, where s is the interlayer spacing (6.6 Å).

According to Halperin *et al.* [29], the criterion for the Josephson junctions to become effectively insulating is $R_\perp > R_Q$, where $R_Q = h/(4e^2) = 6.45$ kΩ is the quantum of resistance for Cooper pairs. We define H_Q as the field at which $R_\perp = R_Q$. In Fig. 3, we show that $R_\perp/R_Q$ scales as $[(H_\perp - H_c^\perp)/(H_Q - H_c^\perp)]^{\alpha(T)}$, with the T dependence of the exponent α displayed in the inset; the T dependences of $H_c^\perp$ and H_Q are shown in Fig. 1(a). The scaling is motivated by a calculation from Konik [30] for $\rho_\perp$ in a model of weak Josephson coupling between 2D layers; he predicts $\alpha_{\rm K} = \frac{3}{4}[1 + (T_{c0} - T)/T_{c0}]$. To partially compensate for changes in the field dependence on converting from $\rho_\perp$ to $R_\perp$, the dotted line in the inset corresponds to $\alpha_{\rm K} + 0.5$.

In Fig. 4 we compare the temperature dependence of $\rho_\perp$ and $\rho_\parallel$ in high fields. For $\rho_\perp$, the field appears to shift the superconducting transition to low temperature. In contrast, $\rho_\parallel$ shows a substantial drop near 30 K even in the highest field, and it continues towards zero on further cooling. To emphasize this behavior, the inset of Fig. 4(b) shows the ratio of finite differences $\Delta\rho_\parallel/\Delta T$, as a function of field and temperature. For $\mu_0 H_\perp \gtrsim 1$ T, one can see that the maximum of this approximate derivative occurs at 30 ± 2 K, which we identify as $T_c^{\rm 2D}$, the onset of mean-field 2D-like superconductivity [31]. The finite

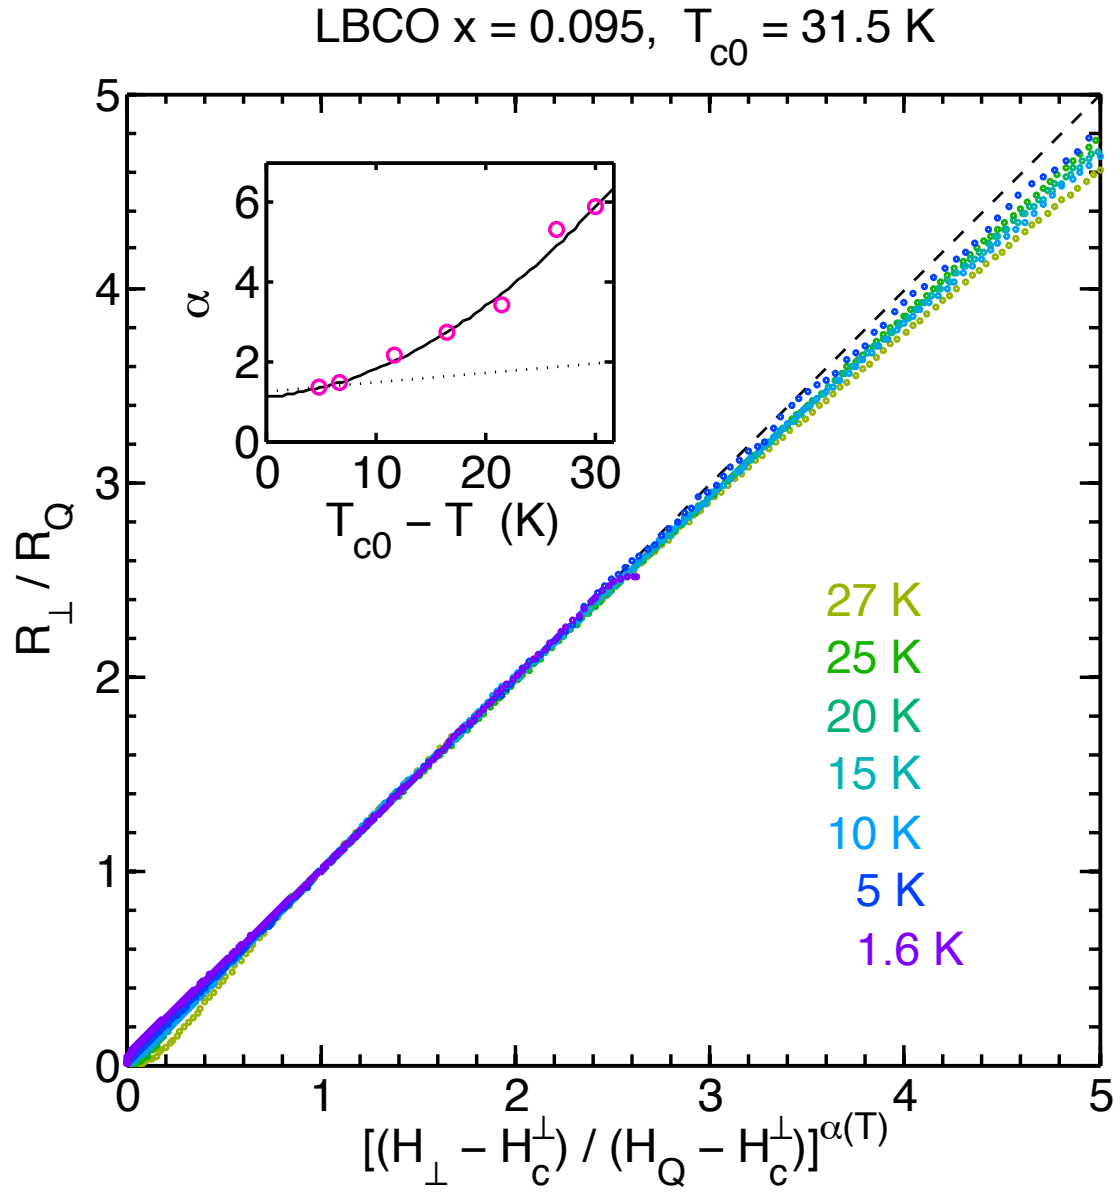

FIG. 3. (color online) Plot of $R_\perp/R_Q$ vs. $[(H_\perp - H_c^\perp)/(H_Q - H_c^\perp)]^{\alpha(T)}$, as described in the text, for data at temperatures from 1.6 to 27 K. The dashed straight line is for reference. The T dependence of the exponent α is plotted in the inset. Dotted line represents $\alpha_K + 0.5$, as described in the text; solid line corresponds to $\alpha = 1.1 + 0.75t + 4.5t^2$, with $t = (T_{c0} - T)/T_{c0}$.

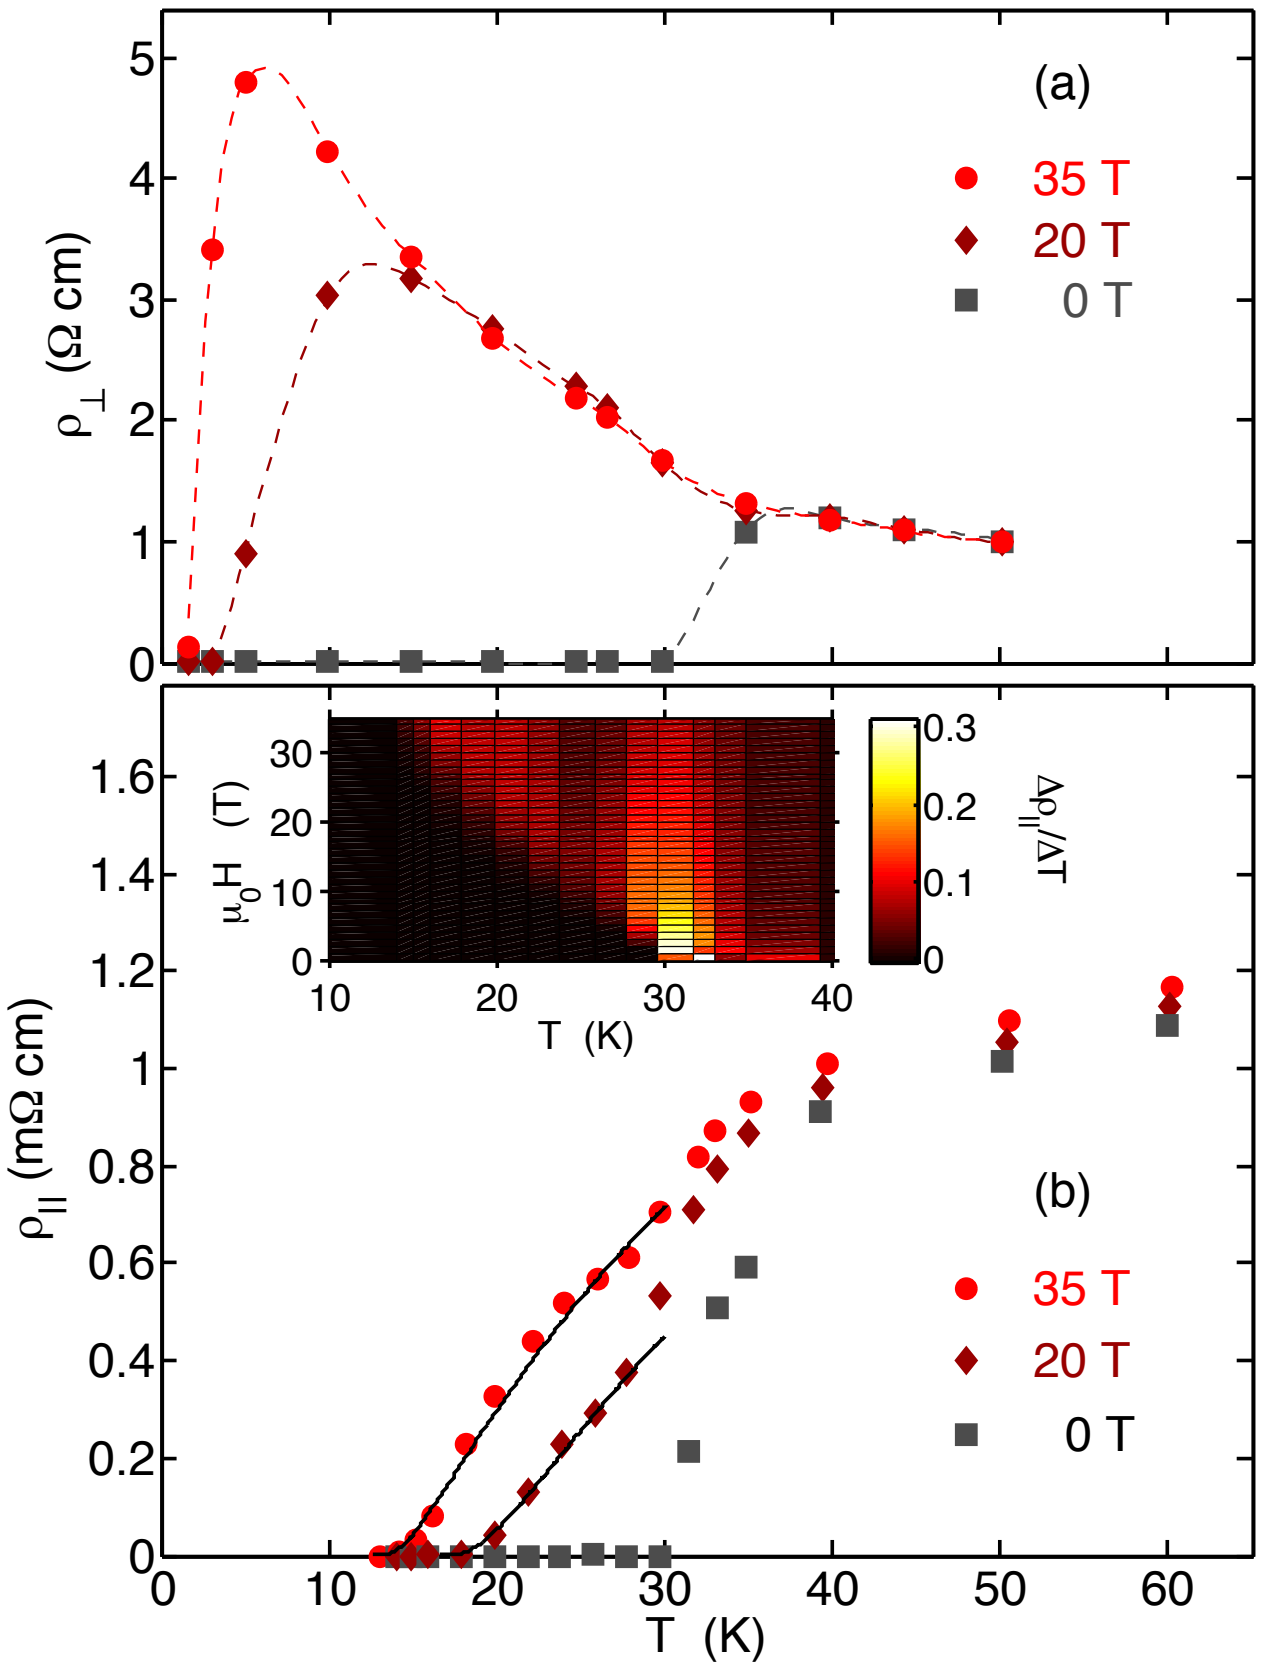

FIG. 4. (color online) Measurements of (a) $\rho_\perp$ and (b) $\rho_\parallel$ as a function of temperature for $\mu_0 H_\perp = 0$, 20, and 35 T. The dashed lines in (a) are guides to the eye. The solid lines in (b) are calculations of 2D flux-flow resistivity, as discussed in the text. Inset of (b) shows $\Delta\rho_\parallel/\Delta T$ as a function of $H_\perp$ and T.

resistivity at lower temperature indicates a lack of phase order, as we discuss next.

In zero field, a 2D superconductor has zero resistivity only below the Berezinskii-Kosterlitz-Thouless transition, $T_{\rm BKT}$, as above that temperature depairing of vortex-antivortex excitations destroys the phase coherence [16, 17]. The resistivity, which is proportional to the product of the density of free vortices and the vortex mobility, is predicted [5, 15] to have the form

$$\rho_\parallel/\rho_{\parallel,n} = a e^{-b/\tau^\gamma}, \qquad (1)$$

where $\rho_{\parallel,n}$ is the normal-state resistivity, $\tau = T/T_{\rm BKT} - 1$, a and b are constants of order one, and $\gamma = 0.5$. In the mixed state, the applied $H_\perp$ will increase the density of free vortices, and hence will increase the resistivity [32, 33]. In a study of 2D-like superconductivity in LBCO $x = 1/8$ [1], it was found empirically that $\rho_\parallel(T)$ in a field could still be described by Eq. (1), provided that one takes account of the reduction of $T_{\rm BKT}$ by the field. Theoretically, one does not expect $T_{\rm BKT}$ to remain finite in the mixed state of a 2D superconductor [11]; however, our system is never truly 2D. We have a stack of 2D layers, and the electromagnetic interaction between pancake vortices in neighboring layers provides some interlayer coupling, allowing a BKT-like transition in the zero-field limit [10].

To apply Eq. (1), we need an estimate for $\rho_{\parallel,n}$. We choose to use a linear extrapolation of $\rho_\parallel$ fit to data at $T \geq 50$ K for $\mu_0 H_\perp = 35$ T. Using this, we obtain the curves through the 20 and 35-T data in Fig. 4(b), with parameters $T_{\rm BKT} = 16.5$ and 12.5 K, respectively, $a = 2.5$ and $b = 1.5$; here and in the following we set $\gamma = 0.6$ to improve the agreement with the data. We can use the same formula to compare with $\rho_\parallel(H_\perp)/\rho_{\parallel,n}$ of Fig. 5, provided that we insert the field dependence through $T_{\rm BKT}(H_\perp)$; the latter corresponds to $H_c^\parallel(T)$ of Fig. 1(b). We get an initial estimate $H_c^{\parallel i}(T)$ from the field at which $\rho_\parallel/\rho_{\parallel,n}$ falls below 10^{-3}, yielding the (black) squares in Fig. 5. To account for the finite cutoff, we make the adjustment $\mu_0 H_c^\parallel = \mu_0 H_c^{\parallel i} - C_i/T$ with $C_i = 44.8\,$T K. Inverting, we fit $T_{\rm BKT}$ with a cubic poynomial in $H_\perp$. The curves calculated with Eq. (1) are indicated by the solid (black) lines in Fig. 5, where we have used the same fixed values of a, b, and γ. Although there is no theoretical justification for it, we find that Eq. (1) provides a consistent fit to the data with few parameters.

To review, we see in Fig. 4 that cooling from the normal state in a large $H_\perp$ results in a drop in $\rho_\parallel$ at $T_c^{\rm 2D} \approx 30$ K, while the temperature dependence of $\rho_\perp$ has insulating character. The drop in $\rho_\parallel$ must be due to superconduct-

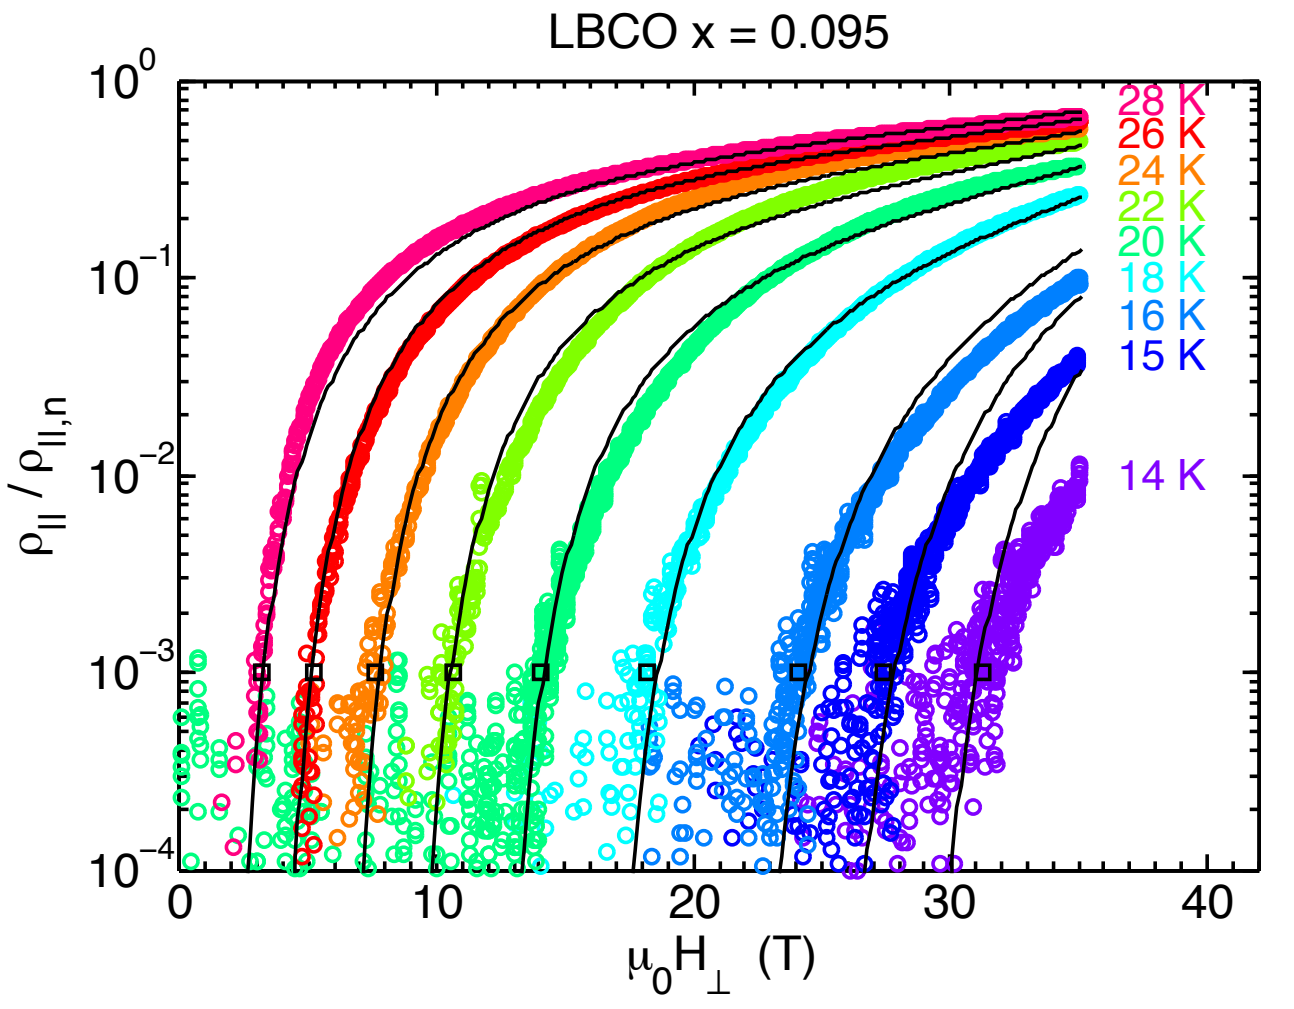

FIG. 5. (color online) Plot of $\rho_{\|}(H_\perp)$ normalized to approximate normal-state values (see text). Squares indicate fields at which data cross 10^{-3}. Solid lines are calculations using Eq. (1), as discussed in the text.

ing correlations, which are only apparent for transport parallel to the $\mathrm{CuO_2}$ layers. Thus, it seems reasonable to interpret $T_c^{\rm 2D}$ as the onset of mean-field superconductivity within Josephson-decoupled 2D layers, just as occurs at 40 K (in zero field) for LBCO $x = 1/8$ [1]. With further cooling, or on reducing the field, the resistivity decreases in a fashion that is qualitatively consistent with expectations for vortex-liquid behavior in the layers. The sharp drop in $\rho_{\|}$ on reducing $H_\perp$, shown in Fig. 5, strongly suggests a transition from a vortex liquid to a vortex solid state [34].

A vortex-liquid state has previously been proposed to explain features of the pseudogap phase at $T > T_{c0}$ [35, 36]. Along with other recent work [37, 38], our results suggest that such a scenario is overly optimistic. The rise of $\rho_{\|}$ on warming through $T_c^{\rm 2D}$ indicates a loss of uniform superconducting correlations in the normal state. T_{c0} is slightly larger than $T_c^{\rm 2D}$, suggesting that, upon cooling in zero field, 3D order develops just before the individual layers would become superconducting in the absence of Josephson coupling, as others have observed in $\mathrm{Bi_2Sr_2CaCu_2O_{8+\delta}}$ [39–41].

Observation of the LVL (and the LPD-SC) is only possible when the interlayer Josephson coupling is frustrated. We note that one proposed origin of the frustration is the development of pair-density-wave (PDW) order in association with charge and spin stripe order [7, 8, 42]. Neutron and x-ray diffraction measurements on LBCO $x = 0.095$ have demonstrated that both charge and spin stripe order are enhanced by $H_\perp$ for $T \lesssim T_c^{\rm 2D}$ [12]; however, it should be noted that, while the occurrence of PDW order would explain the loss of 3D superconducting order, it would not, by itself, explain the apparent stability of the LPD-SC state in large $H_\perp$.

The modulated pair wave function of the PDW state provides a way for the superconductivity to coexist with local antiferromagnetic order: the superconducting wave function has zeros at the extrema of the spin density wave, and vice versa. This is consistent with experimental evidence that long-range commensurate antiferromagnetic order and superconductivity do not coexist in LBCO or $\mathrm{La_{2-x}Sr_xCuO_4}$ [43–45]. At the same time, the modulation makes the PDW state quite sensitive to disorder, consistent with the strongly depressed bulk T_c in LBCO $x = 1/8$. For $x = 0.095$, the superconducting order develops at much higher T_{c0} and T_c^{2D} is virtually independent of $H_\perp$ even for $\mu_0 H_\perp$ as high as 35 T. The stability indicates that there are at least quantitative differences from $x = 1/8$. Nevertheless, it will be shown elsewhere [46] that, even in zero field, the low-energy incommensurate spin fluctuations are gapless and that there is no sign of a conventional spin resonance. Is there any solution other than a spatially-modulated superconducting state that could coexist in this material with gapless, spatially-modulated spin fluctuations?

We thank E. Fradkin, S. A. Kivelson, R. M. Konik, and A. Tsvelik for stimulating discussions and valuable guidance. The work at Brookhaven was supported by the Center for Emergent Superconductivity, an Energy Frontier Research Center funded by the Office of Basic Energy Sciences (BES), Division of Materials Science and Engineering, U.S. Department of Energy, through Contract No. DE-AC02-98CH10886. The NHMFL is supported by the State of Florida and the National Science Foundation's Division of Materials Research through DMR-0654118.

[1] Q. Li, M. Hücker, G. D. Gu, A. M. Tsvelik, and J. M. Tranquada, Phys. Rev. Lett. **99**, 067001 (2007).
[2] J. M. Tranquada, G. D. Gu, M. Hücker, Q. Jie, H.-J. Kang, R. Klingeler, Q. Li, N. Tristan, J. S. Wen, G. Y. Xu, Z. J. Xu, J. Zhou, and M. v. Zimmermann, Phys. Rev. B **78**, 174529 (2008).
[3] A. R. Moodenbaugh, Y. Xu, M. Suenaga, T. J. Folkerts, and R. N. Shelton, Phys. Rev. B **38**, 4596 (1988).
[4] M. Hücker, M. v. Zimmermann, G. D. Gu, Z. J. Xu, J. S. Wen, G. Xu, H. J. Kang, A. Zheludev, and J. M. Tranquada, Phys. Rev. B **83**, 104506 (2011).
[5] B. I. Halperin and D. R. Nelson, J. Low Temp. Phys. **36**, 599 (1979).
[6] Y. Imry, Phys. Rev. B **13**, 3018 (1976).
[7] A. Himeda, T. Kato, and M. Ogata, Phys. Rev. Lett. **88**, 117001 (2002).
[8] E. Berg, E. Fradkin, E.-A. Kim, S. A. Kivelson, V. Oganesyan, J. M. Tranquada, and S. C. Zhang, Phys. Rev. Lett. **99**, 127003 (2007).
[9] S. Tajima, T. Noda, H. Eisaki, and S. Uchida, Phys. Rev. Lett. **86**, 500 (2001).
[10] K. S. Raman, V. Oganesyan, and S. L. Sondhi, Phys. Rev. B **79**, 174528 (2009).

[11] D. S. Fisher, M. P. A. Fisher, and D. A. Huse, Phys. Rev. B **43**, 130 (1991).

[12] J. Wen, Q. Jie, Q. Li, M. Hücker, M. v. Zimmermann, S. J. Han, Z. Xu, D. K. Singh, R. M. Konik, L. Zhang, G. Gu, and J. M. Tranquada, Phys. Rev. B **85**, 134513 (2012).

[13] J. Wen, Z. Xu, G. Xu, Q. Jie, M. Hücker, A. Zheludev, W. Tian, B. L. Winn, J. L. Zarestky, D. K. Singh, T. Hong, Q. Li, G. Gu, and J. M. Tranquada, Phys. Rev. B **85**, 134512 (2012).

[14] M. Tinkham, Phys. Rev. Lett. **61**, 1658 (1988).

[15] J. M. Kosterlitz, J. Phys. C **7**, 1046 (1974).

[16] V. L. Berezinskii, Zh. Eksp. Teor. Fiz. **61**, 1144 (1971).

[17] J. M. Kosterlitz and D. J. Thouless, J. Phys. C **6**, 1181 (1973).

[18] C. C. Homes, M. Hücker, Q. Li, Z. J. Xu, J. S. Wen, G. D. Gu, and J. M. Tranquada, Phys. Rev. B **85**, 134510 (2012).

[19] N. Morozov, L. Krusin-Elbaum, T. Shibauchi, L. N. Bulaevskii, M. P. Maley, Y. I. Latyshev, and T. Yamashita, Phys. Rev. Lett. **84**, 1784 (2000).

[20] T. Shibauchi, L. Krusin-Elbaum, M. Li, M. P. Maley, and P. H. Kes, Phys. Rev. Lett. **86**, 5763 (2001).

[21] S. Ono, Y. Ando, F. F. Balakirev, J. B. Betts, and G. S. Boebinger, Phys. Rev. B **70**, 224521 (2004).

[22] M. A. Steiner, G. Boebinger, and A. Kapitulnik, Phys. Rev. Lett. **94**, 107008 (2005).

[23] H. Aubin, C. A. Marrache-Kikuchi, A. Pourret, K. Behnia, L. Bergé, L. Dumoulin, and J. Lesueur, Phys. Rev. B **73**, 094521 (2006).

[24] H. Q. Nguyen, S. M. Hollen, M. D. Stewart, J. Shainline, A. Yin, J. M. Xu, and J. M. Valles, Phys. Rev. Lett. **103**, 157001 (2009).

[25] G. Briceño, M. F. Crommie, and A. Zettl, Phys. Rev. Lett. **66**, 2164 (1991).

[26] K. E. Gray and D. H. Kim, Phys. Rev. Lett. **70**, 1693 (1993).

[27] K. Kadowaki, S. L. Yuan, K. Kishio, T. Kimura, and K. Kitazawa, Phys. Rev. B **50**, 7230(R) (1994).

[28] J. D. Hettinger, K. E. Gray, B. W. Veal, A. P. Paulikas, P. Kostic, B. R. Washburn, W. C. Tonjes, and A. C. Flewelling, Phys. Rev. Lett. **74**, 4726 (1995).

[29] B. I. Halperin, G. Refael, and E. Demler, "Resistance in Superconductors," in *BCS: 50 Years*, edited by L. N. Cooper and D. Feldman (World Scientific, 2010) Chap. 10.

[30] R. M. Konik, (manuscript in preparation).

[31] We note that there is also structure in $\rho_{\|}(T)$ for zero field and $T > T_c$; however, that is associated with 3D superconducting fluctuations as discussed in [13].

[32] S. Doniach and B. A. Huberman, Phys. Rev. Lett. **42**, 1169 (1979).

[33] P. Minnhagen, Phys. Rev. B **23**, 5745 (1981).

[34] If the layers were completely decoupled, then our observations would be in conflict with the accepted theoretical expectations for a layered superconductor in a strong transverse field [47]; hence, we infer a residual interlayer coupling of an unconventional type.

[35] P. W. Anderson, Nat. Phys. **3**, 160 (2007).

[36] Z. Tešanović, Nat. Phys. **4**, 408 (2008).

[37] L. S. Bilbro, R. Valdés Aguilar, G. Logvenov, I. Bozovic, and N. P. Armitage, Phys. Rev. B **84**, 100511(R) (2011).

[38] J. Mosqueira, J. D. Dancausa, and F. Vidal, Phys. Rev. B **84**, 174518 (2011).

[39] J. Corson, R. Mallozzi, J. Orenstein, J. N. Eckstein, and I. Bozovic, Nature **398**, 221 (1999).

[40] Y. M. Wan, T. R. Lemberger, S. E. Hebboul, and J. C. Garland, Phys. Rev. B **54**, 3602 (1996).

[41] S. Weyeneth, T. Schneider, and E. Giannini, Phys. Rev. B **79**, 214504 (2009).

[42] E. Berg, E. Fradkin, S. A. Kivelson, and J. M. Tranquada, New J. Phys. **11**, 115004 (2009).

[43] R. J. Birgeneau, C. Stock, J. M. Tranquada, and K. Yamada, J. Phys. Soc. Jpn. **75**, 111003 (2006).

[44] I. Bozovic, G. Logvenov, M. A. J. Verhoeven, P. Caputo, E. Goldobin, and T. H. Geballe, Nature **422**, 873 (2003).

[45] A. Suter, E. Morenzoni, T. Prokscha, B. M. Wojek, H. Luetkens, G. Nieuwenhuys, A. Gozar, G. Logvenov, and I. Božović, Phys. Rev. Lett. **106**, 237003 (2011).

[46] Z. J. Xu, C. Stock, A. Kolesnikov, G. D. Gu, and J. M. Tranquada (unpublished).

[47] A. E. Koshelev, Phys. Rev. Lett. **76**, 1340 (1996).